THERMAL PLASMA TORCHES FOR METALLURGICAL APPLICATIONS

L. Rao, *P. Carabin

PyroGenesis Canada Inc.,
1744 rue William,
Suite 200, Montreal, QC, H3J 1R4
*(*Corresponding author: pcarabin@pyrogenesis.com)*

ABSTRACT

Advances in thermal plasma torches have resulted in this technology becoming a commercially viable solution for chemical and metallurgical processes. The main advantages of plasma are its ability to control process chemistry and to build small footprint reactors due to its high energy density and reactivity of the free radicals that are produced. This paper focuses on thermal plasmas produced by DC torches and their applications for waste treatment, production of high purity metals, and nanomaterials. Both transferred and non-transferred torches have been used as either a source of heat or as a reagent in various industrial processes.

Towards Clean Metallurgical Processing for Profit, Social and Environmental Stewardship
Proceedings of the 51st Annual Conference of Metallurgists of CIM (COM 2012)
Niagara, ON, Canada
Edited by
R.H. Schonewille, D. Rioux, S. Kashani-Nejad, M. Kreuh, M.E.S. Muinonen

INTRODUCTION

Plasma technology has become an ideal solution for many industrial chemical, metallurgical and mechanical processes (Venkataramani, 2002). Thermal plasma powered systems are typical used for their unique characteristics such as high energy densities, high temperatures, small installation sizes, rapid start-up and shutdown features, controlled process chemistry and use of electrical energy as a heating source resulting in decoupling the heat source from the oxygen flow rate (Heberlein et al., 2007). Depending on the nature of the main plasma forming gas used, thermal plasma systems offer a high temperature heating source coupled with a highly reactive plasma plume rich in free radicals and ions which promote otherwise hard to drive chemical reactions, as well as high heat transfer rates.

Industrial plasmas can be broadly classified as thermal plasmas and non thermal plasmas. Thermal plasmas are atmospheric pressure plasmas characterized by local thermodynamic equilibrium (Boulos et al., 1994). Thermal plasmas are typically established between any two current conducting electrodes separated by an insulator. A plasma forming gas is blown between the two conducting electrodes resulting in a high temperature plasma plume. A plasma torch generates and maintains an electrically conducting gas column between the two electrodes; a cathode (negative electrode) and an anode (positive electrode) (Camacho, 1988). If both electrodes are housed in a single housing, resulting in an arc enclosed inside the plasma torch, then such plasma generating torches are termed as non-transferred (NT) plasma torches, whereas, if the second electrode is external to the torch, creating an arc transferred between the cathode and the working piece, then such plasma torches are termed as transferred (T) plasma torches. Depending on the source of the electricity which can be either direct current (DC), alternating current (AC) at main network frequency or at radio frequency (RF), the plasma torches are classified as DC, AC or RF plasma torches (Venkataramani, 2002).

For the past 20 years, PyroGenesis Canada Inc., (PCI) has been developing non transferred direct current plasma torches and has been using them for a wide range of applications. This paper focuses on the design, characteristics and typical applications of the plasma torches developed by PCI.

PCI DEVELOPED NON TRANSFERRED PLASMA TORCHES

PCI has been developing and marketing non transferred DC plasma torch systems for some of the most demanding applications. PCI has developed a series of different thermal plasma torch systems namely:

i) Compact coaxial plasma torch (Minigun™)
ii) Reverse polarity high enthalpy plasma torch – RPT™
iii) Air Plasma Torch – APT™
iv) Steam Plasma Torch – SPT™

Each of these torch designs, their typical characteristics and their applications are described below.

COMPACT COAXIAL PLASMA TORCH (MINIGUN™) DESIGN, CHARACTERISTICS AND TYPICAL APPLICATIONS

Figure 1 shows a picture of the assembled compact coaxial plasma torch (Minigun™). This plasma torch consists of co-axial mounted refractory metal lined copper electrodes, which are water cooled. A stainless steel body houses the co-axially mounted electrodes along with the water cooling channels and gas flowing conduits, carved out of high temperature plastic such as Ultem™. A self sustaining plasma column is established between a pen shaped button cathode and a tubular shaped anode and is stabilised with vortex generators. This plasma torch design does not employ an external magnetic field to stabilize the plasma arc column, keeping the torch extremely compact. Powered from a DC source, this plasma torch works with any oxygen free inert gas, such as argon, nitrogen, helium, hydrogen, methane and/or a mixture of the above gases, as the plasma forming gas. The maximum gross power of this plasma torch is

dependent upon the working gas used i.e., if pure argon is used as the plasma forming gas then this torch can delivery a maximum power of 50 kW however, if a mixture of argon and hydrogen is used as the plasma forming gas, under similar operating conditions, it can deliver a maximum gross power of 80 kW.

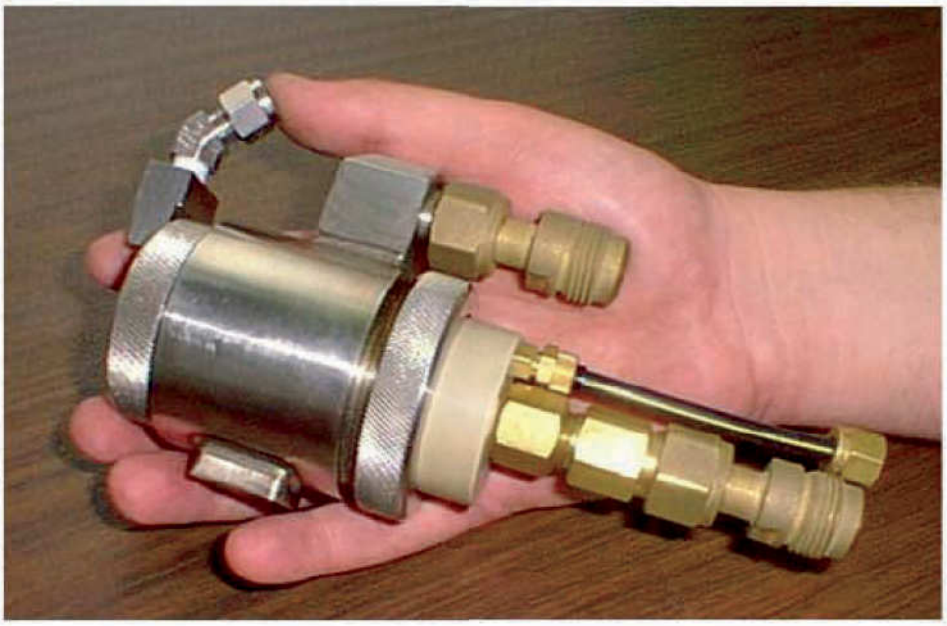

Figure 1 – A picture of the assembled compact coaxial plasma torch (Minigun)

This plasma torch design offers many advantages such as:

i) Compact design i.e., 60 mm diameter (2.5 inches) and a minimum length of 80 mm (3 inches), making ideally suited for thermal spray applications in hard to reach areas, for example to apply thermal barrier coatings to paper machine dryer cans.
ii) Easy connections with only two connections for water-cooled power cables (one for each DC phase), and one connection for plasma forming gas.
iii) High thermal efficiency reaching up to 70%,
iv) A wide range of torch power turn down ratio ranging from 2.5 kW gross power to 60 kW gross power,
v) Long electrode life with electrodes lasting over 1000 hrs,
vi) Ability to run on many inert gases and their mixtures, and
vii) Wide range of plasma plume enthalpy.

Figure 2 shows a graph of plasma torch gross power vs. plasma plume enthalpy for pure argon as the plasma forming gas. As shown in Figure 2, when operated with pure argon as working gas, this plasma torch can be operated in a wide range of plasma plume enthalpy ranging from 7.4E+05 J/kg to 6.8E+06 J/kg. This unique feature of this plasma torch design makes it an ideal solution for research and development environments which requires a wide range of torch gross power and plasma plume enthalpy.

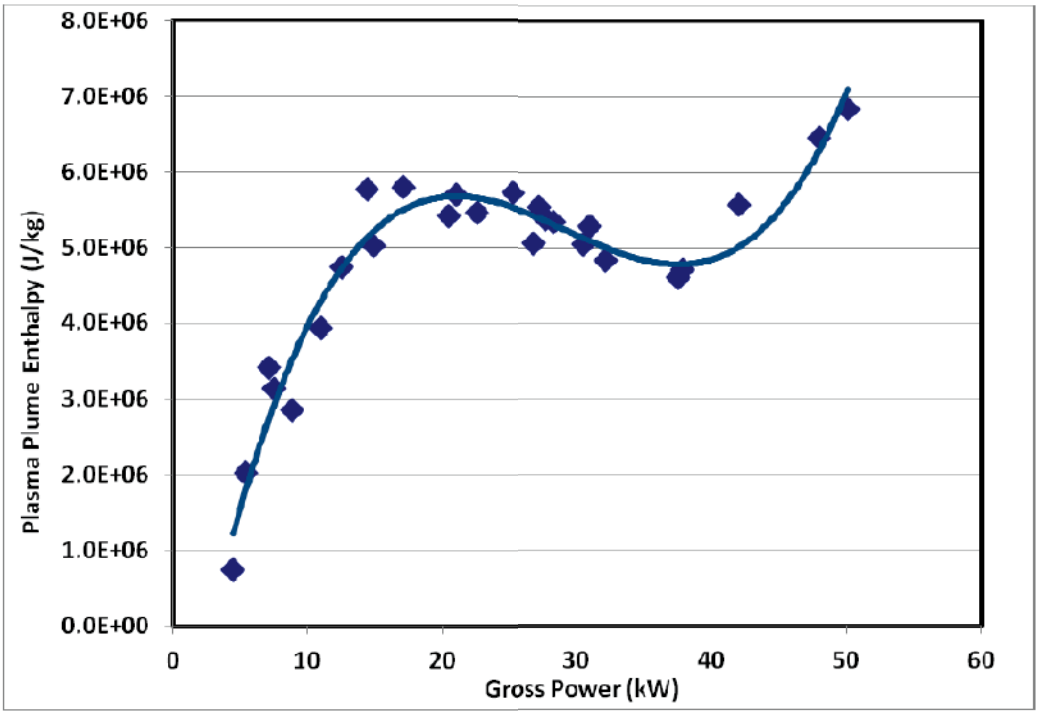

Figure 2 – Gross power vs. plasma plume enthalpy for compact coaxial plasma torch (Minigun) with pure argon as the plasma forming gas

This plasma torch which was originally designed for thermal spray applications can be used in many applications. In additions to its use in thermal spray coating in hard to access locations, this plasma torch can be employed in small scale waste treatment applications, thermal processing, small scale advanced materials production, production of nanomaterials and research and development applications. For example, Figure 3 shows a SEM micrograph of a nanometric metallic salt which was produced using Minigun.

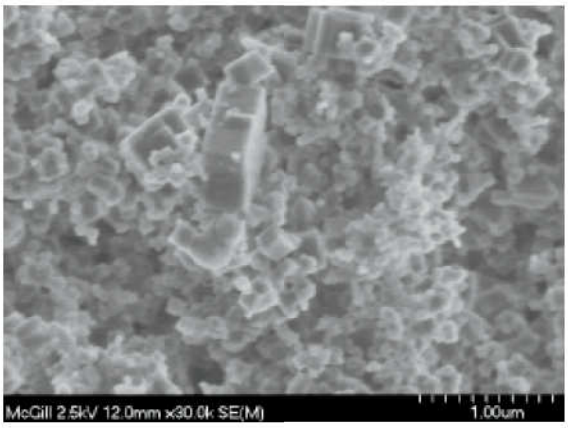

Figure 3 – SEM micrograph of the nanometric metallic salt

REVERSE POLARITY HIGH ENTHALPY PLASMA TORCH (RPT™) DESIGN, CHARACTERISTICS AND TYPICAL APPLICATIONS

Figure 4 shows a picture of the assembled reverse polarity high enthalpy plasma torch. This plasma torch consists of co-axial mounted refractory metal lined copper electrodes, which are water cooled. A stainless steel body houses the co-axially mounted electrodes along with the water cooling channels and gas flowing conduits, carved out of high temperature plastic such as Vespel™. A self sustaining plasma column is established between a tubular cathode and a tubular shaped anode and is stabilised using gas vortex generators. Similar to the Minigun design, this plasma torch design does not require any external magnetic fields to stabilize the arc column. Powered from a DC source, this plasma torch works with any oxygen free inert gas, such as argon, nitrogen, helium and/or a mixture of the above gases, as the plasma forming gas. Similar to the Minigun design, the maximum gross power of this plasma torch is dependent upon the working gas used i.e., if pure argon is used as the plasma forming gas then this torch can delivery a maximum power of 80 kW however, if a mixture of argon and hydrogen is used as the plasma forming gas, under similar operating conditions, it can deliver a maximum gross power of 100 kW.

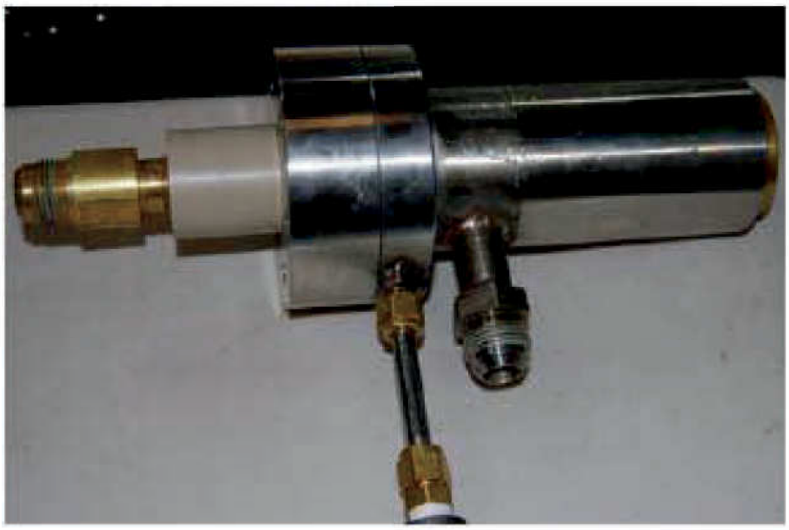

Figure 4 – A picture of the assembled reverse polarity high enthalpy plasma torch

The RPT™ plasma torch design offers many advantages such as:

i) High thermal efficiency reaching up to 70%,
ii) A wide range of torch power turn down ratio ranging from 5 kW gross power to 80 kW gross power,
iii) Long electrode life with electrodes lasting over 1000 hrs,
iv) Low erosion rates, on the order of 0.01 ng/C at 40 kW, making it ideal for high purity material production
v) Ability to run on many inert gases and their mixtures, and
vi) High enthalpy plasma plume, almost double that of the Minigun™.

Figure 5 shows a graph of plasma torch gross power vs. plasma plume enthalpy for pure argon as the plasma forming gas. As shown in Figure 5, when operated with pure argon as working gas, this plasma torch can be operated at high plasma plume enthalpy above 5.6E+06 J/kg up to 1.7E+07 J/kg. This feature of this plasma torch design is used for applications which require higher plasma plume enthalpies such as the production of carbon nano tubes (CNT's) (Harbec et al, 2004; Harbec et al, 2011).

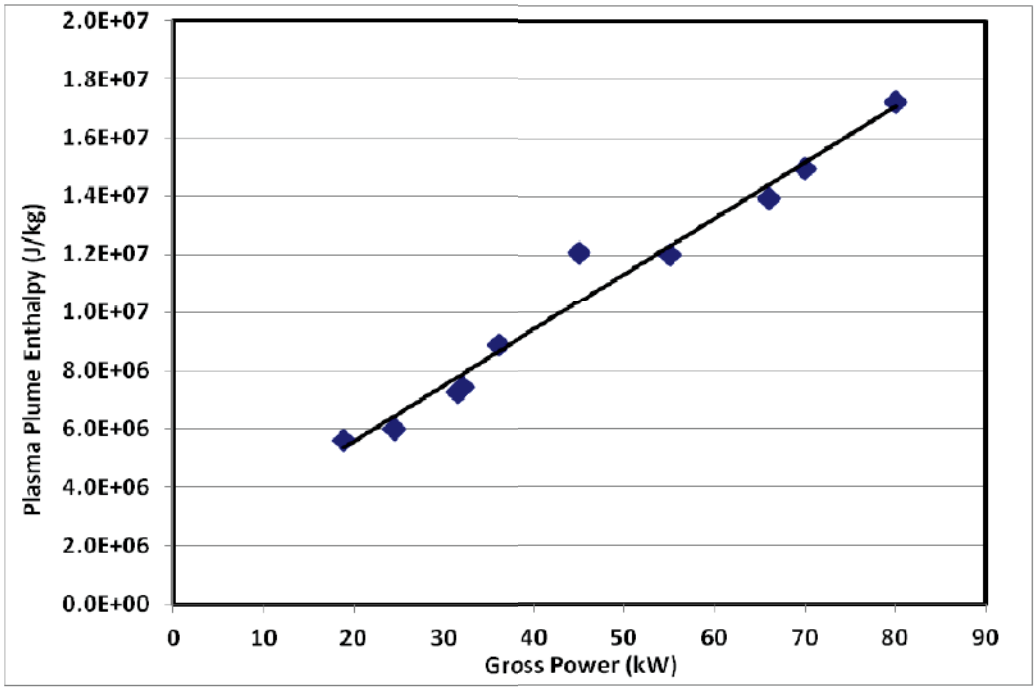

Figure 5 – Gross power vs. plasma plume enthalpy for reverse polarity high polarity plasma torch with pure argon as the plasma forming gas

This RPT™, because of its ability to provide high plasma plume enthalpies, is chiefly employed in applications which require very high energy densities such as production on CNT's, fullerenes, nano metallic powders and in small scale waste treatment applications, and research and development applications. For example, Figure 6 shows an example of spherical metallic powders produced using the RPT (Smagorinski et al., 2002) and Figure 7 shows an example of carbon nanotubes produced with an RPT torch.

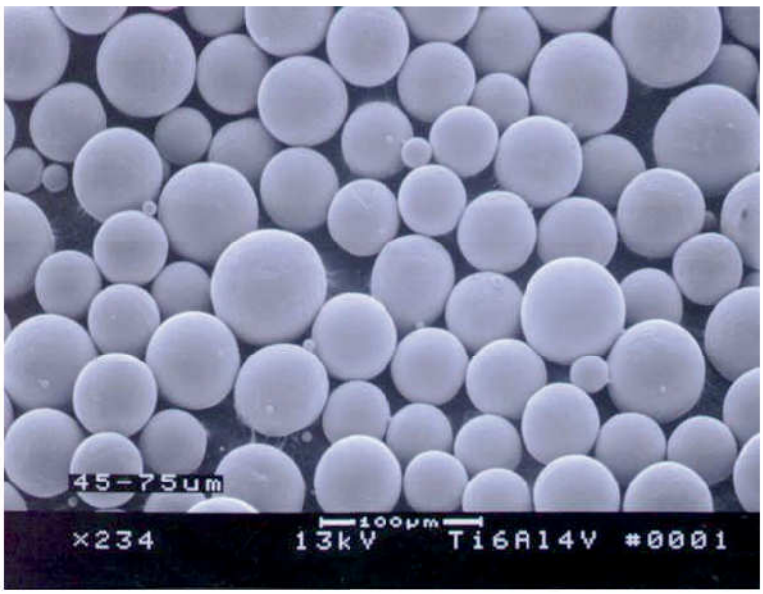

Figure 6 – Spherical metallic powders produced using RPT™ plasma torch

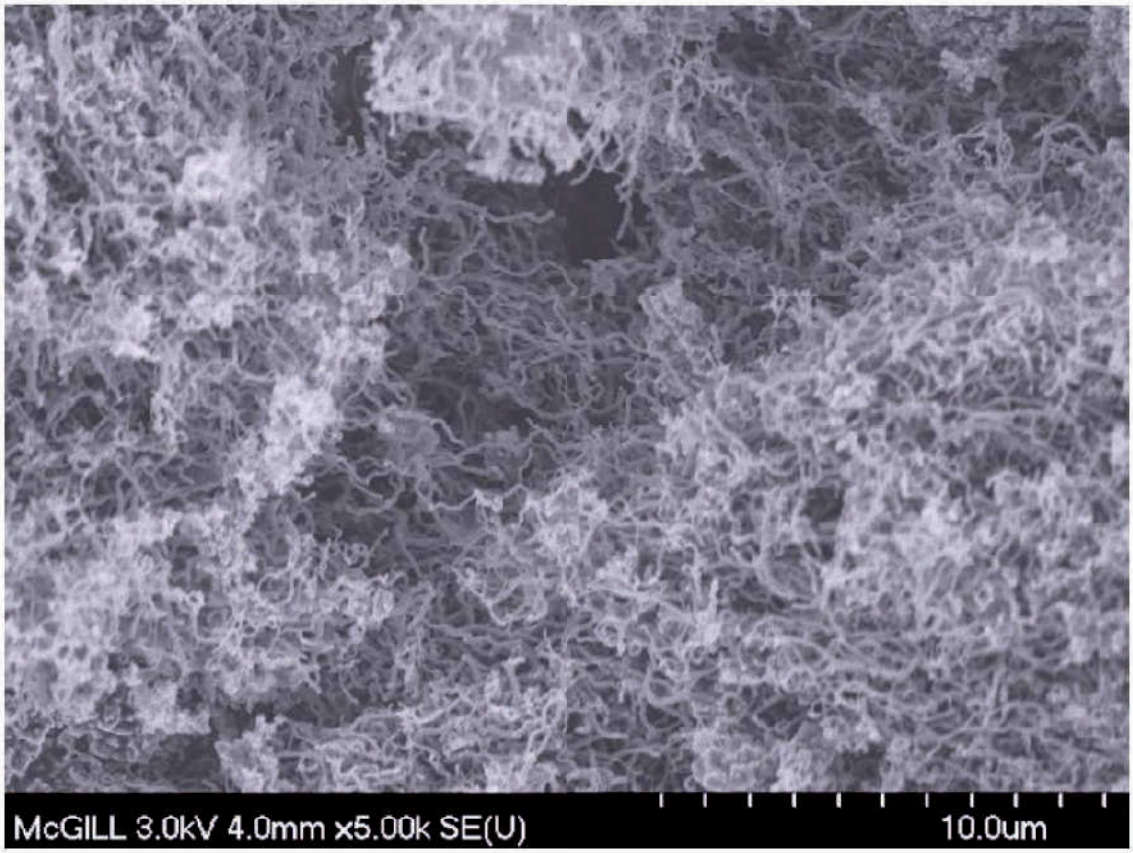

Figure 7 – Carbon nanotubes produced with an RPT torch (photo courtesy of McGill University)

AIR PLASMA TORCH (APT™) DESIGN, CHARACTERISTICS AND TYPICAL APPLICATIONS

Figure 8 shows a picture of the assembled air plasma torch. This plasma torch consists of three electrodes namely, a pen shaped refractory metal lined copper cathode, a tubular copper ignition electrode and a tubular copper anode. All three electrodes are water cooled using high pressure deionised water flowing in a closed circuit. A stainless steel body houses the co-axially mounted electrodes along with the water cooling channels and gas flowing conduits, carved out of high temperature plastic such as Ultem™. A self sustaining plasma column is ignited between the cathode and the ignition electrode and is transferred to the working anode. Any oxygen free inert gas such nitrogen and/or argon is used as a shroud gas to protect the refractory metal lined cathode. The main plasma forming which is air is introduced between the ignition electrode and the working anode, through a swirl generator, consisting of tangentially drilled holes. The shroud gas typically represents 10% by volume of the main plasma forming gas. Powered by a DC source, this plasma torch typically works with compressed air as the main plasma forming gas.

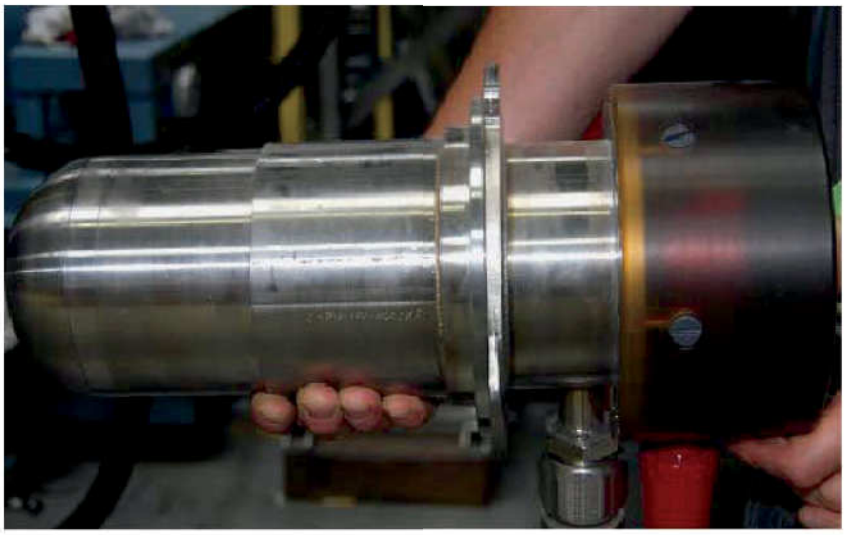

Figure 8 – A picture of the assembled air plasma torch

This plasma torch design offers many advantages such as:

i) High thermal efficiency reaching up to 70%,
ii) A wide range of torch power turn down ratio ranging from 50 kW gross power to 500 kW gross power,
iii) Long electrode life with electrodes lasting over 1000 hrs for the cathode and ignition anode, 600 hours for the main anode

Figure 9 shows a graph of the plasma torch gross power vs. plasma plume enthalpy. As shown in Figure 9, this plasma torch design offers various ranges of plasma plume enthalpy, ranging form 2 to 4 kWh/kg, running on air as the plasma forming gas. Hence, depending on process requirement, enthalpy could be doubled.

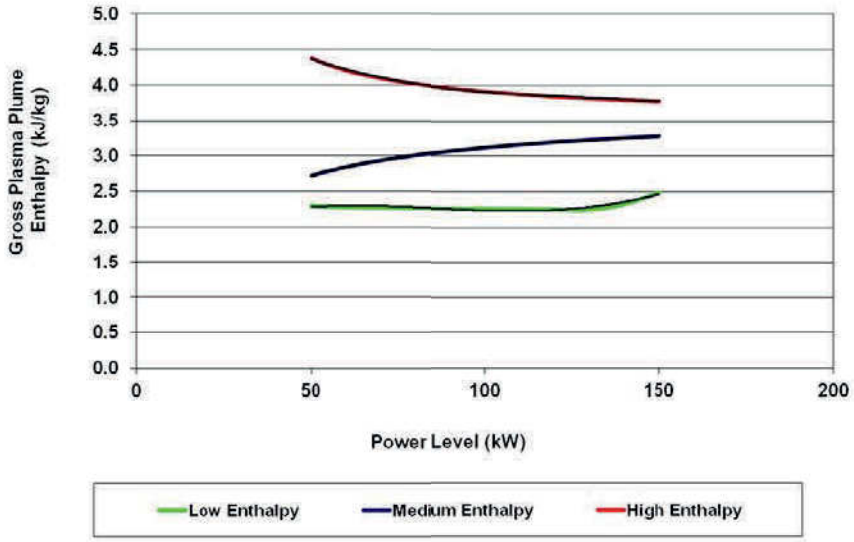

Figure 9 – Gross power vs. plasma plume enthalpy for air plasma torch

This plasma torch design was originally developed for waste treatment applications from PCI. PCI has successfully used this plasma torch design in its Plasma Arc Waste Destruction System (PAWDS) and in Plasma Resource Recovery Systems (PRRS) for waste combustion and waste to energy applications respectively (Heberlein and Murphy, 2008). In addition to its application for waste treatment, this plasma torch system can be used for other applications such as gas heating (Camacho, 1988), plasma assisted ignition and combustion of coal (Sligar, 1990), plasma melting, scrap melting (Maske et al., 1983), ladle heating, chemical synthesis and plasma cutting and welding applications (Venkataramani, 2002).

STEAM PLASMA TORCH AND TYPICAL APPLICATIONS OF STEAM PLASMA TORCH

This plasma torch consists of three electrodes namely, a pen shaped refractory metal lined copper cathode, a tubular copper ignition electrode and a tubular copper anode. All three electrodes are water cooled using high pressure deionised water flowing in a closed circuit. A stainless steel body houses the co-axially mounted electrodes along with the water cooling channels and gas flowing conduits, carved out of high temperature plastic such as Ultem™. A self sustaining plasma column is ignited between the cathode and the ignition electrode and is transferred to the working anode. Any oxygen free inert gas such nitrogen and/or argon is used as a shroud gas to protect the refractory metal lined cathode. The steam plasma torch is ignited on air and then gradually switched to steam torch. The main plasma forming is introduced between the ignition electrode and the working anode, through a swirl generator, consisting of tangentially drilled holes. Powered from a DC source, this plasma torch works with super heated steam as the plasma forming gas and can operated between 50 kW to 150 kW gross power.

This plasma torch design offers many advantages such as:

i) A wide range of torch power turn down ratio ranging from 50 kW gross power to 150 kW gross power,
ii) Long electrode life with electrodes lasting over 200 hrs for the anode and 1000 hrs for the ignition electrode and the cathode.

This plasma torch design was originally developed for destruction of hard to destroy hazardous substances such as halogenated hydrocarbons such as chlorofluorocarbons and brominated hydrocarbons. PCI has successful demonstrated that the steam plasma torch can be used to destroy R-12 refrigerants to a destruction and removal efficiency of 99.9999%. Other potential applications of steam plasma torch include, steam reforming (Zhu et al., 2011), coal gasification, steam arc cutting [Pauser et al., 1999], rapid decontamination of large surfaces (Farrar et al., 2000) etc.

CONCLUSIONS

An overview of PyroGenesis DC torches and their applications was presented for use in waste treatment, production of high purity metals, and nanomaterials.

The Minigun™ uses any non oxygen containing gas as a plasma forming gas. Originally designed for thermal spray applications, it can be used in many applications such as small scale waste treatment applications, thermal processing, small scale advanced materials production, and production of nanomaterials

The RPT™ provides twice the enthalpy level of the Minigun™ and also runs with any non oxygen containing gas as a plasma forming gas. It boasts very low erosion rates, making it very useful in the production of high purity materials.

The APT™ was originally developed for waste treatment. It typically uses air as the main plasma forming gas, but, due to the use of a shroud gas for the cathode, allows for a wide choice of plasma forming gas, including oxidizing gases. In addition to its application for waste treatment, this plasma torch

system can be used for other applications such as gas heating, plasma assisted ignition and combustion, plasma melting, scrap melting, ladle heating, and chemical synthesis.

The SPT™ uses steam (water vapour) as the main plasma forming gas. The high reactivity of the hydroxyl ions produced by the ionization of steam allows for the destruction of highly stable hazardous substances such as chlorofluorocarbons and brominated hydrocarbons. Other applications of steam plasma include; steam reforming, coal gasification, steam arc cutting, and rapid decontamination of large surfaces.

REFERENCES

Boulos, M.I., Fauchais, O., and Pfender, E., 1994. Thermal plasmas: fundamentals and applications. Volume 1, Plenum Press, New York, NY, 452 p.

Camacho, S.L., 1988. Industrial-worthy plasma torches: state of the art. Pure and Applied Chemistry. Vol. 60. No. 5. p. 619-632.

Farrar, L.C., Haack, D.P., Mcgrath, S.F., Dickens, J.C., O'hair, E.A. and Fralick, J.A., 2000. Rapid decontamination of large surface areas. IEEE Transactions on Plasma Science, Vol. 28, No. 1.

Harbec, D., Meunier, J-L., Guo, L., Gauvin, R. and Mallah, N., 2004. Carbon nanotubes from the dissociation of C_2Cl_4 using a DC thermal plasma torch. Journal of Physics D: Applied Physics, Vol. 37, p. 2121–2126.

Harbec, D. and Meunier, J.-L., 2011. Growth of carbon nanotubes above the peritectic temperature of tungsten metal catalyst. Carbon, Vol. 49, issue 7, June 2011, p. 2206-2215.

Heberlein, J. and Murphy, A.B., 2008. Thermal plasma waste treatment. Journal of Physics D: Applied Physics, Vol. 41.

Maske, K.U. and Barcza, N.A., 1983. Recent development in pyrometallurgical plasma technology. Proceedings of Innovation In Processing Ores and Scraps.

Pauser, H., Laimer, J. and Stori, H. 1999. Steam plasma arc cutting. IEEE International Conference on Plasma Science, p. 319.

Sligar, J., 1990. Plasma ignition of pulverised coal. Proceedings of the 25th Intersociety Energy Conversion Engineering Conference, IECEC-90, 12-17 Aug 1990, p. 454 - 458.

Smagorinski, M.E. and Tsanrizos, P.G., 2002. Production of spherical titanium powder by plasma atomization. Proceedings of PM2TEC Conference, Orlando, USA, p.3 – 248-260.

Venkataramani, N., 2002. Industrial plasma torches and applications. Current Science, Vol. 83, No. 3.

Zhu, X., Hoang, T., Lobban, L.L. and Mallinson, R.G., 2011. Plasma steam reforming of E85 for hydrogen rich gas production. Journal of Physics D: Applied Physics, Vol. 44.